arXiv:1303.6325v2 [cond-mat.supr-con] 27 Mar 2013

TAO pairing: a fully gapped pairing scenario for the Iron-Based Superconductors

T. Tzen Ong[1] and Piers Coleman[1, 2]

[1] *Center for Materials Theory, Department of Physics & Astronomy,*
Rutgers University, Piscataway NJ 08854, USA
[2] *Department of Physics, Royal Holloway,*
University of London, Egham, Surrey TW20 0EX, UK

(Dated: March 28, 2013)

Abstract

Motivated by the fully gapped superconductivity in iron-based superconductors with uncompensated electron pockets, we propose a spin-singlet analogue of the superfluid phase of ^{3}He-B. We show that the staggered tetrahedral structure of these systems with 2 iron-atoms per unit cell introduces additional site and orbital band indices τ and α which act as internal isospin degrees of freedom, opening up a new class of tetrahedral and orbital ("TAO") triplet condensates. This permits two locally d-wave pairings to combine in quadrature without breaking lattice or time reversal symmetry, to produce a fully gapped topological superconductor. The internal chirality of this state is selected by a Josephson coupling between the d-wave components. This state is predicted to give rise to Raman-active excitations associated with the reversal of the gap chirality.

The discovery of superconductivity with $T_c = 26\text{K}$ in LaFeAsO by Hosono *et. al.*[1] has opened a new field of iron (Fe)-based multi-band high temperature superconductors (SCs)[2, 3]. Transport and ARPES experiments consistently show that these systems are fully gapped, while optical measurements also show a significant Coulomb interaction[4]. Most electronically mediated superconductors, avoid the onsite Coulomb interactions by building nodes into the pair wave, so that we expect the onsite pairing $\langle\psi_\uparrow\psi_\downarrow\rangle_{\text{Fe}} = \int_{\mathbf{k}} \frac{\Delta_{\mathbf{k}}}{2E_{\mathbf{k}}} = 0$. In the organic, heavy fermion, cuprate and strontium ruthenate superconductors, this "Coulomb orthogonalization" is guaranteed by a d- or p-wave symmetry of the order parameter[5–9].

Superconductivity in the Fe-based systems is widely believed to derive from a gap function with $s^{\pm}$ symmetry [2, 10], where the gap takes the form $\Delta(\mathbf{k}) = \Delta_0 + 2\Delta_1 \cos k_x \cos k_y$, giving rise to a gap node between the electron and hole pockets. This is supported by experiments showing c-axis Josephson tunneling[11] and QPI measurements on Fe(Se,Te) [12], including absence of the Wohlleben effect in SQUID measurements[13]. In this scenario, a phase cancellation between the electron and hole pockets eliminates on-site pairing, minimizing the Coulomb interaction. However, when the hole pockets are absent, such as in $\text{A}_x\text{Fe}_2\text{Se}_2$ [14] and single layer FeSe [15], the node in the $s^{\pm}$ order parameter is expected to intersect the the electron pockets to achieve Coulomb orthogonalization. These nodes have not been observed. Another possibility is that the symmetry of the order parameter changes in the electron pocket materials, for example by the development of d-wave pairing, with nodes lying between the pockets [16]; yet this scenario appears to be inconsistent with the observation of small fully gapped hole pockets around the Z-point in $\text{Tl}_{0.63}\text{K}_{0.37}\text{Fe}_{1.78}\text{Se}_2$ [17].

These observations motivate us to seek an alternative description of the of the pairing symmetry which can account for the Coulomb orthogonalization in both the electron-hole and single electron-pocket materials without a change in condensate symmetry. In this search, we are inspired by superfluid ^{3}He-B, where the Fermi surface is fully gapped, yet the pair wavefunction eliminates local pairing through the formation of p-wave spin triplet pair condensate. In two-dimensional ^{3}He-B, the gap function takes the form $\langle c_{\mathbf{k}\sigma} c_{-\mathbf{k}\sigma'}\rangle = (k_x\sigma_x + k_y\sigma_y)i\sigma_2$; although the odd-parity k_x and k_y triplet components contain nodes, their anti-commuting spin structure causes them to add in quadrature to create a fully gapped condensate where $\Delta(\mathbf{k}) \propto [k_x^2 + k_y^2]$. While the spin-triplet scenario is ruled out in iron-based superconductors by Knight-shift measurements [18, 19], the multi-band nature of the iron-based superconductors may offer an analogous route to a fully gapped condensate, for as we now show there are two additional quantum numbers, $\tau = \pm 1$ and $\alpha = \pm 1$, arising from orbital and lattice symmetries, which open up a new class of non-trivial triplet states.

The staggered tetrahedral structure of the iron based superconductors results in an enlarged unit cell containing two rotated Fe tetrahedra. The site index associated with this novel structure plays the role of an additional internal "tetrahedral" index $\tau = \pm 1$ labeling electrons on iron sites within "right" or "left" pointing tetrahedra (Fig. 1.) The Pauli isospin linking these states will be denoted by $\vec{\tau} = (\tau_1, \tau_2, \tau_3)$. Likewise, we associate a quantum number $\alpha = \pm 1$ with the two degenerate zx ($\alpha = +1$) and zy ($\alpha = -1$) d-orbitals of the iron sites, denoting the Pauli matrices that link these states by $\vec{\alpha} = (\alpha_1, \alpha_2, \alpha_3)$ (Fig. 1.).

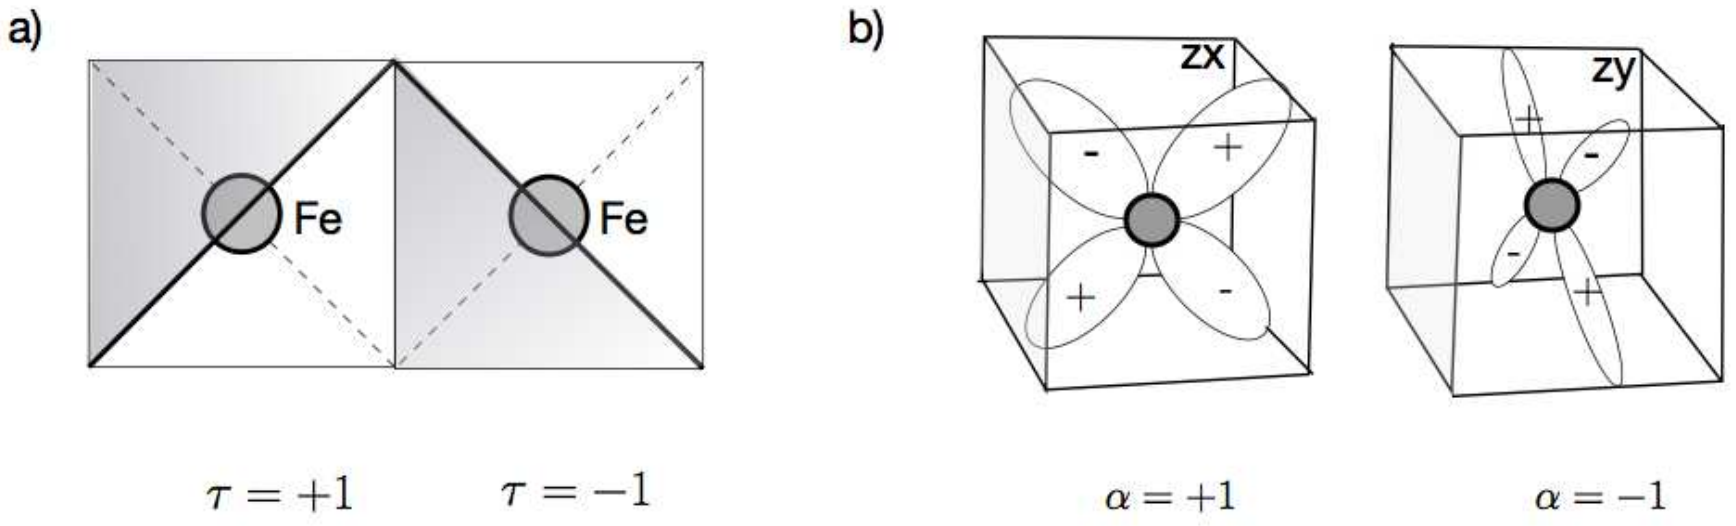

FIG. 1. (a) Tetrahedral index $\tau = \pm 1$ denotes Fe in right or left pointing tetrahedra, (b) orbital index $\alpha = \pm 1$ denotes zx and zy orbitals.

The electron operators now carry three discrete quantum numbers, so we replace the conventional electron operator $c_{\mathbf{k}\sigma} \to c_{\mathbf{k}\nu}$, where $\nu \equiv (\tau, \alpha, \sigma)$ denotes the triplet of site, orbital and spin indices. Since we are treating orbital triplets, we adopt a generalized Balian-Werthamer spinor to describe the electron fields

$$\Psi_{\mathbf{k}} \equiv \begin{pmatrix} \psi_{\mathbf{k}\nu} \\ -i(\lambda_2)_{\nu\nu'}\psi^{\dagger}_{-\mathbf{k}\nu'} \end{pmatrix} \tag{1}$$

where $\lambda_2 = \tau_2\alpha_2\sigma_2$ flips the tetrahedral, orbital and spin quantum numbers so that the electron and hole fields transform the same way under the various isospin rotations. In this notation an extended $s^{\pm}$ pair, written $\Delta^{s\pm}(\mathbf{k}) = cos(k_x)cos(k_y)\tau_2\alpha_2\mathbf{1}_{\sigma}$, is an orbital and site triplet, the orbital analog of equal spin triplet pairing, for once multiplied by λ_2, it is diagonal in site and orbital indices. We now consider a more general class of orbital triplet pairing.

The 2D Fe As(Se) layer exhibits C_{4v} symmetry about the As(Se)atoms, but the two iron atoms in the unit cell lie at sites of lower symmetry. There is no 90° rotation symmetry about an iron site - instead, the unit cell is invariant under a combined 90° rotation and a translation between the two iron sites. This means that the site and orbital indices must transform non-trivially under symmetry operations of the C_{4v} group. Moreover, the global symmetry of the superconducting state need not correspond to the nominal spatial symmetry of the pairs at the iron sites. Thus for example, one can have a staggered d-wave paired state which has a global s-wave symmetry[20]. Lastly, we note that there is no local inversion symmetry at each iron site; instead the inversion is located mid-way between neighboring Fe atoms.

We shall argue that the strong Coulomb forces at the iron sites favor states with local d-wave symmetry, seeking gap functions which contain terms with both local d_{xy} and $d_{x^2-y^2}$ spatial symmetries coupled to different site and orbital channels. Inspired by ^{3}He-B, the pair wave-function then takes the following form

$$\langle c_{\mathbf{k}\nu} c_{-\mathbf{k}\nu'} \rangle = (\Delta_{xy}(\mathbf{k})\Gamma^1_{\nu\nu''} + \Delta_{x^2-y^2}(\mathbf{k})\Gamma^2_{\nu\nu''})(i\lambda_2)_{\nu''\nu'}, \tag{2}$$

where $\Delta_{xy}(\mathbf{k}) = \Delta_1 \sin k_x \sin k_y$ and $\Delta_{x^2-y^2}(\mathbf{k}) = \Delta_2(\cos k_x - \cos k_y)$ are the xy and $x^2 - y^2$ pair amplitudes and the matrices $\Gamma^{1,2} \in [\tau_a \otimes \alpha_b]$ are tensor products of the site and orbital Pauli matrices. These spin singlet pairs have odd parity under spin exchange, but are even under momentum inversion, site (τ) and orbital (α) exchange, thus preserving the antisymmetry of the wavefunction.

To preserve lattice symmetry, Γ_1 and Γ_2 must belong to the *same* irreducible representation of the D$_{4h}$ group and in addition, both must have the same parity under time-reversal and inversion symmetry. The most important requirement, is that the two d-wave pairing components of the Hamiltonian anti-commute with each other, which guarantees that the two gaps add in quadrature. We call this “tao pairing” (tetrahedral and orbital: $\tau\alpha\sigma$). One of its features is that as in ^{3}He-B, the d-vector $\vec{d}(\mathbf{k}) = (\Delta_{xy}(\mathbf{k}), \Delta_{x^2-y^2}(\mathbf{k}))/|\Delta(\mathbf{k})|$ has *topological* character, in this case, winding twice around the origin as $\mathbf{k}$ runs around the Γ point. The chirality $\nu = -\mathrm{sgn}(\Delta_1\Delta_2)$ of the order parameter in internal tao space is selected by the underlying hamiltonian without breaking any symmetry.

Irred. Rep.	SC State	Local Symmetry	Orbital (α) Symmetry
A_1	$c_x c_y\ \tau_2\alpha_2$	$s^{\pm}$	$11+22$
B_1	$i\Delta_{x^2-y^2}\ \tau_3\alpha_2$	$d_{x^2-y^2}$	$11+22$
B_2	$\Delta_{xy}\ \tau_2\alpha_2$	d_{xy}	$11+22$
A_1	$\Delta_{x^2-y^2}\tau_3\alpha_1$	$d_{x^2-y^2}$	$11-22$
	$i\Delta_{xy}\tau_2\alpha_3$	d_{xy}	$12+21$
A_2	$\Delta_{x^2-y^2}\tau_3\alpha_3$	$d_{x^2-y^2}$	$12+21$
	$i\Delta_{xy}\tau_2\alpha_1$	d_{xy}	$11-22$
A_1^*	$i\Delta_{xyz}\tau_1\alpha_2$	3D staggered d_{xy} ("η")	$11+22$
B_1^*	$\Delta_{xyz}\tau_1\alpha_1$	3D staggered d_{xy}	$11-22$

TABLE I. Symmetry classification of the singlet superconducting order parameters in the Fe-based systems. The non-trivial A_1 and A_2 representations contain two one-dimensional d-wave components that transform identically under the C_{4v} group. The A_1^* and B_1^* representations involve staggered d_{xy} order. The τ_1 operator which implements the staggered pairing is odd-parity under inversions through the center of inversion, so that the "f-wave" combination $\Delta_{xyz}\tau_1 = (\Delta_{xy}\tau_1) \times \sin k_z$ is *even* parity. Since α_2 and τ_2 are odd under time-reversal, the time-reversal invariant combinations $i\alpha_2$ and $i\tau_2$ are used in the pair operator.

Table. I classifies the even-parity order parameters, with nearest or next-nearest neighbor pairing in the Fe-based SCs according to the irreducible representations of the C_{4v} group. Within the A_1 and A_2 symmetry classes there are two one dimensional representations with local d_{xy} and local $d_{x^2-y^2}$ symmetry. Their identical symmetries under C_{4v} means that hopping terms in the Hamiltonian will interconvert the two types of pair, creating an internal Josephson coupling between them. Remarkably, as we shall now show, the resulting presence of two linear combinations of d-wave states with different local spatial symmetries, but the same global symmetries, i.e. the same irreducible representations, leads to the formation of a topologically non-trivial state in which the gaps add in quadrature, eliminating the underlying nodes from the quasiparticle excitation spectrum.

In this paper, we shall focus on the A_1 and A_2 states, which are invariant under inversion symmetry of a single layer. By contrast, the A_1^* and B_1^* representations, which involve staggered d_{xy} pairing, are odd-parity within a single plane. These states can only form a tao state in bulk 3D systems, where the inversion center lies between FeAs(Se) layers; by staggering the d_{xy} pairing between layers, the A_1^* and B_1^* states acquire an additional $\sin k_z$ dependence, restoring the inversion symmetry and giving rise to the $\Delta_{xyz} = (\text{staggered}\,\Delta_{xy}) \times \sin k_z$ form-factor. We note that the A_1^* state corresponds to the η-pairing proposed in [20]. We shall return to disucss this case later in the paper.

Using this scheme, we are able to identify **two** fully gapped 2D tao states, one with A_1 symmetry, the other with A_2 symmetry (see Table. II). In multi-layered iron-based systems, the inversion symmetry of an isolated layer is broken, allowing us to also consider tao states which mix "starred" and "unstarred" representations with opposite in-plane inversion symmetry.

tao state	Irreducible Representation	Description
$\Delta_{xy}\tau_2\alpha_3\gamma_2 + \Delta_{x^2-y^2}\tau_3\alpha_1\gamma_1$	A_1	Uniform orbital triplet.
$\Delta_{xy}\tau_2\alpha_1\gamma_2 + \Delta_{x^2-y^2}\tau_3\alpha_3\gamma_1$	A_2	Uniform orbital triplet.
$\Delta_{xyz}\tau_1\alpha_2\gamma_2 + \Delta_{x^2-y^2}\tau_3\alpha_1\gamma_1$	A_1^*	Staggered d_{xyz} orbital triplet.
$\Delta_{xyz}\tau_1\alpha_1\gamma_1 + \Delta_{x^2-y^2}\tau_3\alpha_2\gamma_2$	B_1^*	Staggered d_{xyz} orbital triplet.

TABLE II. Family of orbital triplet tao superconducting states. The asterix denotes tao-states which break the inversion symmetry of a single FeAs layer. The Nambu matrices acting in particle-hole space are denoted by $\vec{\gamma} = (\gamma_1, \gamma_2, \gamma_3)$.

To illustrate these results, we now carry out a BCS treatment of the A_1 tao paired state (see Table. II), with BCS model

$$H = \sum_{\mathbf{k}} \Psi^\dagger_{\mathbf{k}} h(\mathbf{k}) \Psi_{\mathbf{k}} - \frac{g_1}{N_s} \sum_{\mathbf{k},\mathbf{k}'} b^\dagger_{\mathbf{k}1} b_{\mathbf{k}'1} - \frac{g_2}{N_s} \sum_{\mathbf{k},\mathbf{k}'} b^\dagger_{\mathbf{k}2} b_{\mathbf{k}'2}, \tag{3}$$

where N_s is the number of sites in the lattice and

$$b^\dagger_{\mathbf{k}1} = c^\dagger_{\mathbf{k}\nu} \left[\left(d_{xy}(\mathbf{k}) i\tau_2\alpha_3 \right) i\underline{\lambda}_2 \right]_{\nu\nu'} c^\dagger_{-\mathbf{k}\nu'}, \qquad b^\dagger_{\mathbf{k}2} = c^\dagger_{\mathbf{k}\nu} \left[\left(d_{x^2-y^2}(\mathbf{k}) \tau_3\alpha_1 \right) i\underline{\lambda}_2 \right]_{\nu\nu'} c^\dagger_{-\mathbf{k}\nu'} \tag{4}$$

create the two components of a tao-pair with A_1 symmetry, where $d_{xy}(\mathbf{k})$ and $d_{x^2-y^2}(\mathbf{k})$ are the d-wave form factors. For simplicity, we have omitted interaction terms that mix the the two pair types, since as we shall see, this mixing is already provided by the hopping.

The kinetic part of the Hamiltonian

$$h(\mathbf{k}) = \epsilon_0(\mathbf{k})\gamma_3 + \epsilon_1(\mathbf{k})\tau_1 + \epsilon_3(\mathbf{k})\alpha_1 + \epsilon_4(\mathbf{k})\tau_1\alpha_3\gamma_3, \tag{5}$$

contains the kinetic hopping terms consistent with the symmetries of a single FeAs layer. Denoting $c_l \equiv \cos k_l$ $(l = x, y)$ and $s_l \equiv \sin k_l$ $(l = x, y)$, then $\epsilon_1(\mathbf{k}) = 4t_1(c_x + c_y)$ and $\epsilon_0(\mathbf{k}) = 4t_0 c_x c_y - \mu$ are the intra-orbital (orbitally identical) nearest and next nearest-neighbor hopping, where μ is the chemical potential. The terms $\epsilon_4(\mathbf{k}) = 4t_4(c_x - c_y)$ and $\epsilon_3(\mathbf{k}) = 4t_3 s_x s_y$ are the inter-orbital nearest and next-nearest neighbor hoppings (we shall choose a gauge in which $t_3 t_4 > 0$). These terms act as tetrahedral and orbital fields that split the orbital degeneracy of the electron and hole pockets. The resulting normal state spectrum is given by $\epsilon_{n\alpha}(\mathbf{k}) = \epsilon_n(\mathbf{k}) + \alpha\sqrt{\epsilon_3(\mathbf{k})^2 + \epsilon_4(\mathbf{k})^2}$, where $\epsilon_n(\mathbf{k}) = \epsilon_0(\mathbf{k}) + \mathrm{sgn}(n)\epsilon_1(\mathbf{k})$ and $n, \alpha = \pm 1$ are two sets of band indices. Since $\epsilon_3(\mathbf{k}) = 4t_3 d_{xy}(\mathbf{k})$ and $\epsilon_4(\mathbf{k}) = 4t_4 d_{x^2-y^2}(\mathbf{k})$ have d-wave symmetry, the product of the these terms generates matrix elements that hybridize the two locally d-wave components of an A_1 or A_2 tao pair.

Performing a mean-field decoupling of the interaction, we obtain

$$H = \sum_{\mathbf{k}} \Psi^\dagger_{\mathbf{k}} \mathcal{H}(\mathbf{k}) \Psi_{\mathbf{k}} + N_s \left(\frac{\Delta_1^2}{g_1} + \frac{\Delta_2^2}{g_2} \right) \tag{6}$$

where

$$\mathcal{H}(\mathbf{k}) = h(\mathbf{k}) + \Delta_{xy}(\mathbf{k})\tau_2\alpha_3\gamma_2 + \Delta_{x^2-y^2}(\mathbf{k})\tau_3\alpha_1\gamma_1 \tag{7}$$

is the Nambu Hamiltonian. $\mathcal{H}(\mathbf{k})$ can be diagonalized, giving rise to four separate quasi-particle eigenvalues concentrated around the original electron and hole pockets, given by

$$E^{n\alpha}_{\mathbf{k}} = \left[A_n(\mathbf{k}) + \alpha\sqrt{A_n(\mathbf{k})^2 - \gamma_n(\mathbf{k})^2} \right]^{1/2}, \qquad (n, \alpha = \pm 1) \tag{8}$$

where

$$\begin{aligned} A_n &= \epsilon_n^2 + \epsilon_3^2 + \epsilon_4^2 + \Delta_{xy}^2 + \Delta_{x^2-y^2}^2, \\ \gamma_n^2 &= (\epsilon_n^2 - \epsilon_3^2 - \epsilon_4^2 + \Delta_{xy}^2 + \Delta_{x^2-y^2}^2)^2 + 4(\Delta_{xy}\epsilon_3 - \Delta_{x^2-y^2}\epsilon_4)^2, \end{aligned} \tag{9}$$

and for clarity we have suppressed the explicit momentum labels $\mathbf{k}$. From (8) and (9) we see that $(E^{n+}_{\mathbf{k}} E^{n-}_{\mathbf{k}})^2 = \gamma_n(\mathbf{k})^2 > 0$ is positive definite, so that the excitation spectrum is fully gapped. In fact, there are two types of gap structure, depending on the chirality $\nu = -\mathrm{sgn}(\Delta_1\Delta_2)$ of the gap: for $\nu < 0$, $(\Delta_1, \Delta_2$ in phase), the second term in γ_n vanishes on the Fermi surface and the gap becomes highly anisotropic, almost closing with a very small minimum value $\Delta_{min} \sim \min(\Delta_1, \Delta_2)^2/W$, where W is the bandwidth; for positive chirality $\nu > 0$ $(\Delta_1, \Delta_2$ out-of-phase), all terms in γ_n^2 remain positive, and the gap is weakly anisotropic, with a large minimum value $\Delta_{min} \sim \min(\Delta_1, \Delta_2)$. The large gap, positive chirality state is thus selected by the lattice. Had we not chosen a gauge where $t_3 t_4 > 0$ the selected chirality would be given by $\nu = \mathrm{sgn}(t_3 t_4)$.

Figs. 2 & 3 show the superconducting gaps for the two generic cases seen in the iron-based superconductors; two electron and hole pockets around M and Γ, and also two electron pockets around M, showing the fully gapped structure in both cases. To explore the internal Josephson coupling between the two condensates, we minimize the mean-field Free energy

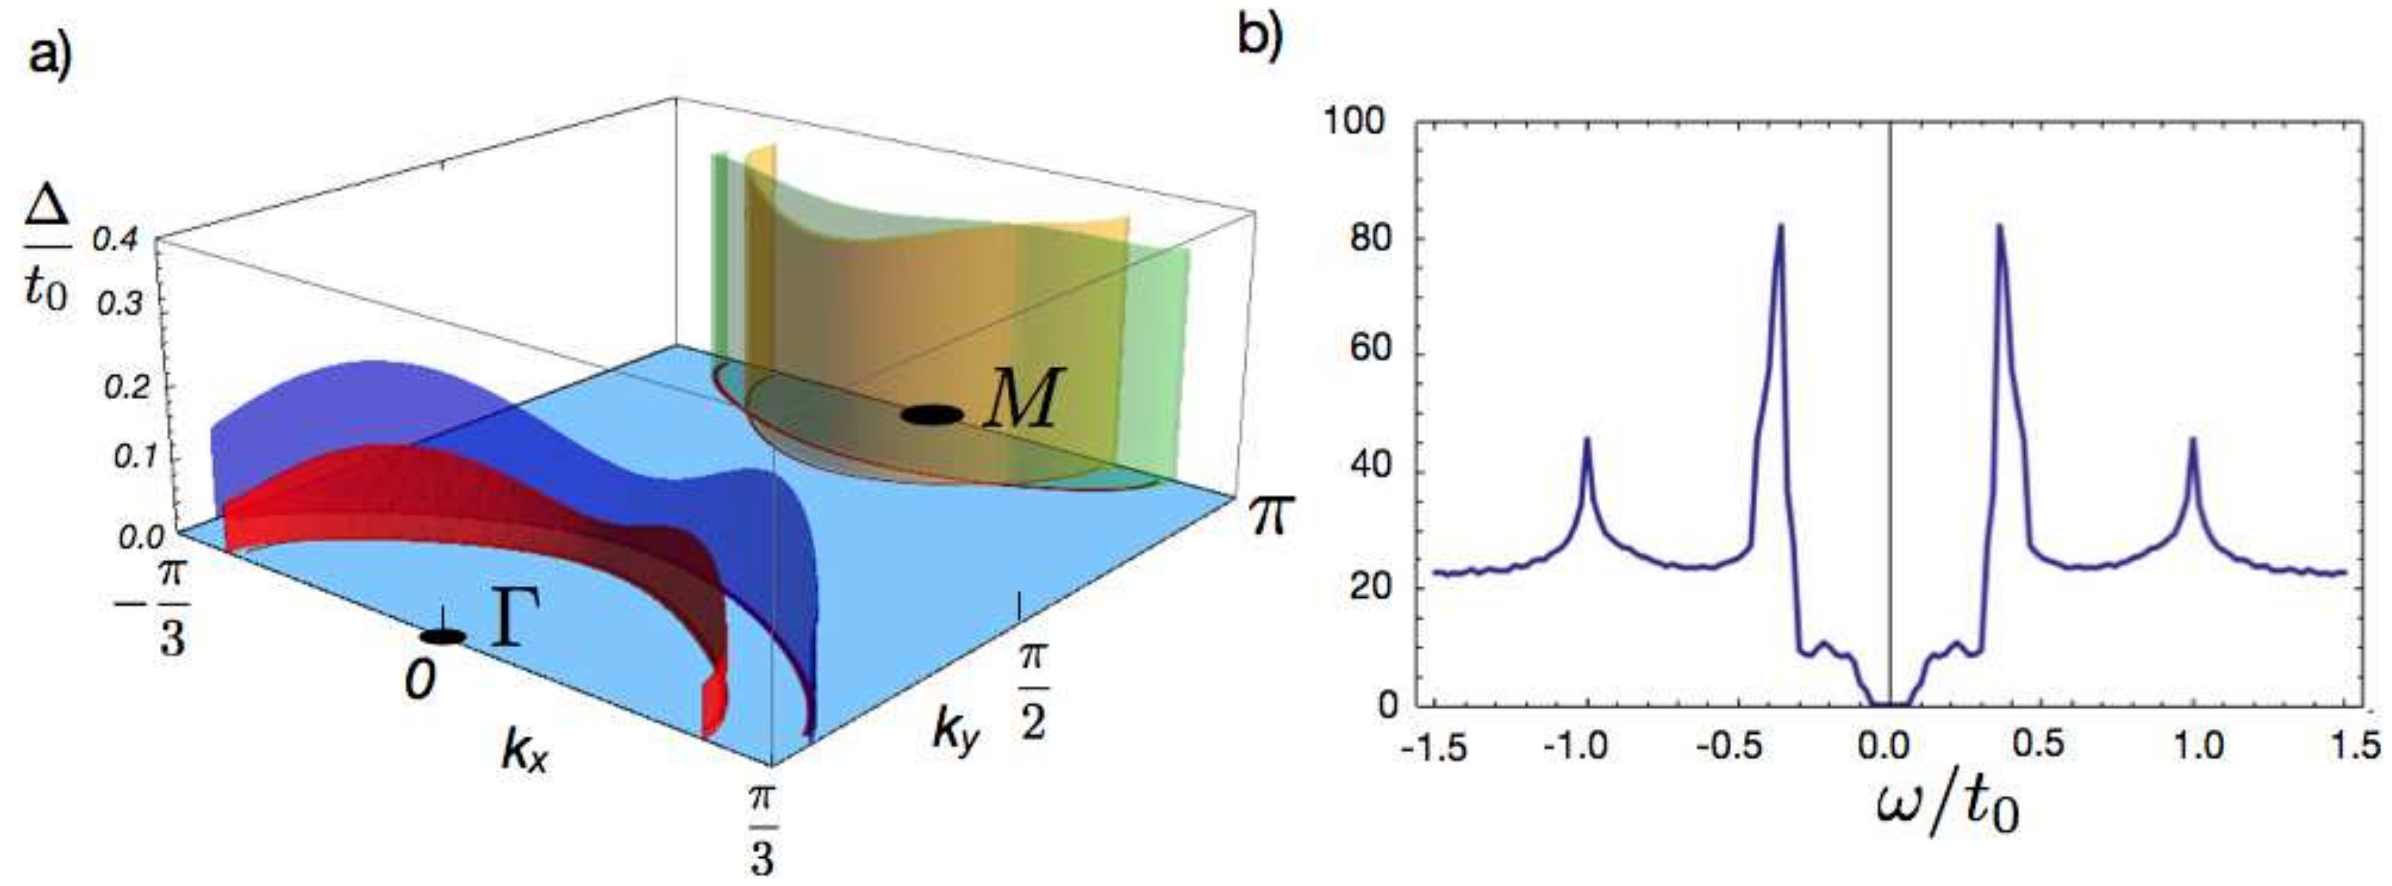

FIG. 2. (a)Superconducting gap of the hole and electron pockets around Γ and M. The Fermi surface contours are shown as red lines, and the superconducting gaps are shown in red and blue for the two hole pockets, and in yellow and green for the electron pockets. (b)The DOS for the superconducting state with a clear gap around E_F. Energies are measured in units of t_0. The parameters used are $t_0 = 1.0, t_1 = 0.1, t_3 = 1.0, t_4 = 0.6, \mu = 0.6, \Delta_1 = 0.5, \Delta_2 = -0.2$.

$$F = N_s \left[\frac{\Delta_1^2}{g_1} + \frac{\Delta_2^2}{g_2}\right] - 2T \sum_{\mathbf{k},n,\alpha} \ln \left[2\cosh\left(\frac{E_{\mathbf{k}}^{n\alpha}}{2T}\right)\right] \tag{10}$$

with respect to Δ_1 and Δ_2, to obtain two coupled gap equations

$$\begin{pmatrix} 1/g_1 - \chi_{xy} & -\chi_J \\ -\chi_J & 1/g_2 - \chi_{x^2-y^2} \end{pmatrix} \begin{pmatrix} \Delta_1 \\ \Delta_2 \end{pmatrix} = 0 \tag{11}$$

where, denoting $\int_{\mathbf{k}} \equiv \int \frac{d^2k}{(2\pi)^2}$ and $B_{\mathbf{k}n} = \sqrt{A_{\mathbf{k}n}^2 - \gamma_{n\mathbf{k}}^2}$,

$$\chi_{xy} = \sum_{n\alpha} \int_{\mathbf{k}} \frac{\mathrm{th}(\beta \mathrm{E}_{\mathbf{k}}^{\mathrm{n}\alpha}/2)}{2E_{\mathbf{k}}^{n\alpha}} \left[1 + 2\alpha \frac{(4t_3 d_{x^2-y^2})^2}{B_{\mathbf{k}n}}\right] d_{xy}^2 \tag{12}$$

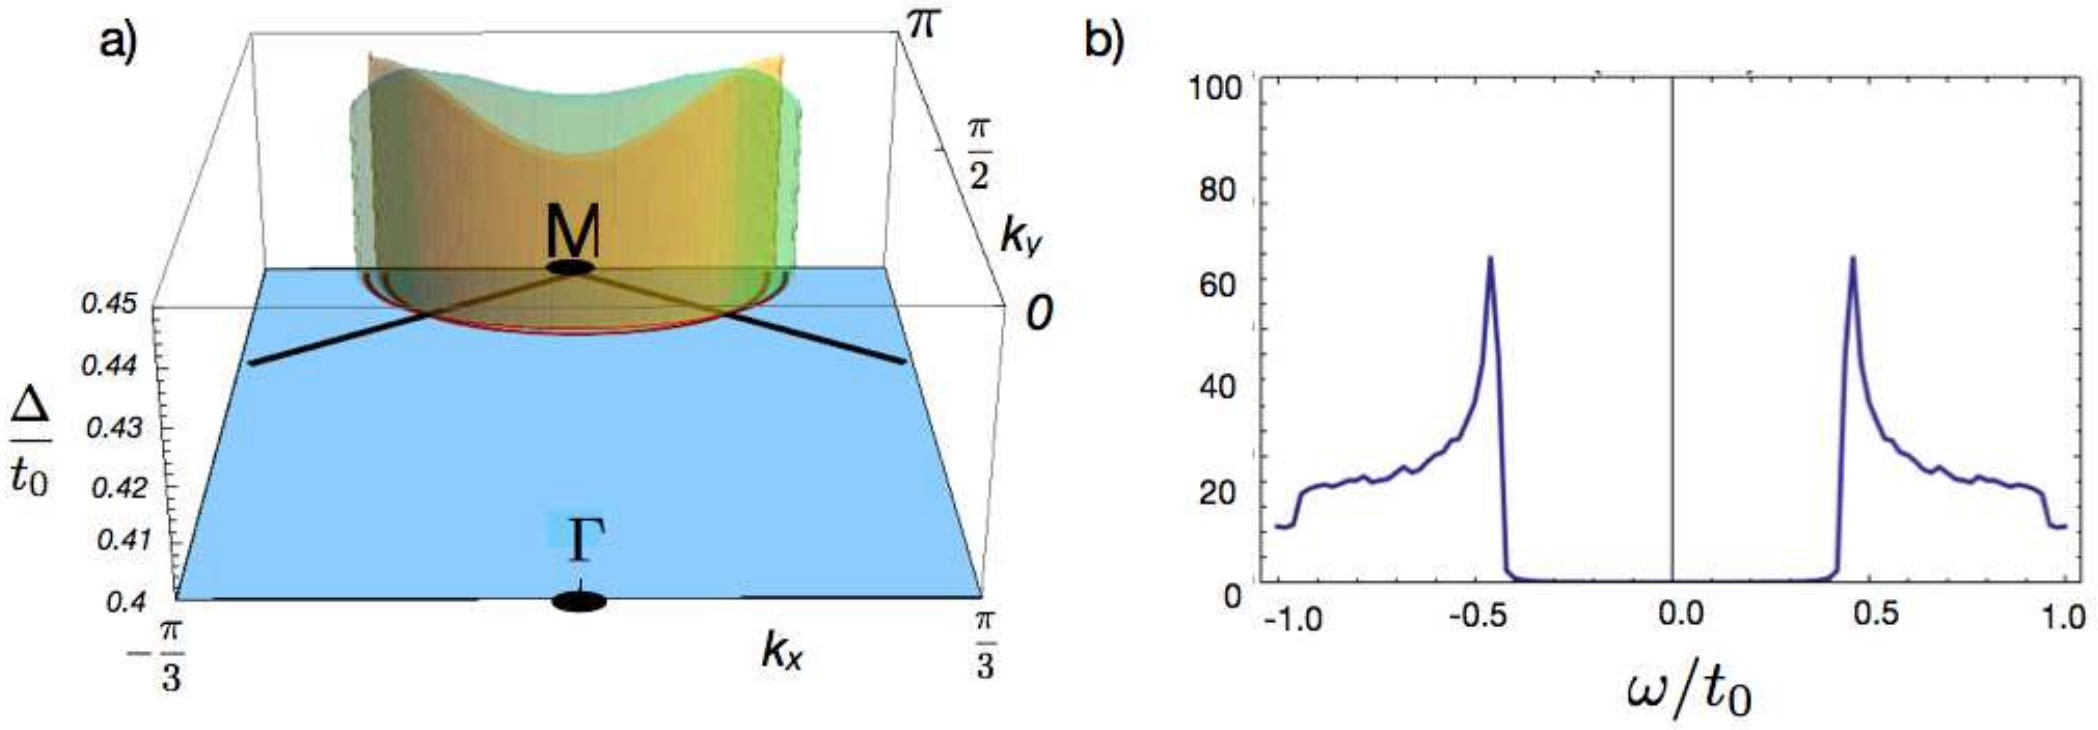

FIG. 3. (a)Superconducting gap for a choice of parameters with only electron pockets around M. The Fermi surface contours are shown as red lines, and the superconducting gaps are shown in yellow and green for the two electron pockets, and the black lines mark the real Brillouin zone. (b)The DOS for the superconducting state with a large gap around E_F. Energies are measured in units of t_0. The parameters used are $t_0 = 1.0, t_1 = 0.15, t_3 = 0.7, t_4 = 0.7, \mu = -4.0, \Delta_1 = 0.5, \Delta_2 = -0.25$.

$$\chi_{x^2-y^2} = \sum_{n\alpha} \int_{\mathbf{k}} \frac{\mathrm{th}(\beta \mathrm{E}^{\mathrm{n}\alpha}_{\mathbf{k}}/2)}{2E^{n\alpha}_{\mathbf{k}}} \left[1 + 2\alpha \frac{(4t_4 d_{xy})^2}{B_{\mathbf{k}n}}\right] d^2_{x^2-y^2} \tag{13}$$

are the d_{xy} and $d_{x^2-y^2}$ pair-susceptibilities, while

$$\chi_J = \sum_{n\alpha} \alpha \int_{\mathbf{k}} \frac{\mathrm{th}(\beta \mathrm{E}^{\mathrm{n}\alpha}_{\mathbf{k}}/2)}{2E^{n\alpha}_{\mathbf{k}}} \left[\frac{2t_3 t_4}{B_{\mathbf{k}n}}\right] (4 d_{xy} d_{x^2-y^2})^2 \tag{14}$$

is the internal Josephson coupling between them. Since the $E^{n\alpha}_{\mathbf{k}}$ have the lowest magnitude when $\alpha = -1$, χ_J is negative, inducing a π coupling between the d-wave condensates, favoring selection of a positive chirality $\nu > 0$. The mean-field transition temperature is determined by $(1/g_1 - \chi_{xy})(1/g_2 - \chi_{x^2-y^2}) - \chi_J^2 = 0$. In a conventional d-wave superconductor, pairing develops exclusively in the single most attractive d-wave channel, but in this system, the strong Josephson coupling between the two states will immediately lock the two gaps into a topological state with a single, enhanced transition temperature. To get an idea of the magnitude of this effect, let us put $\chi_{xy}, \chi_{x^2-y^2} \sim N(0) ln(W/T)$, $\chi_J(T) \sim -\lambda_J \chi_{xy}(T)$, where $N(0)$ is the density of states and λ_J a quantity of order unity, then if $g_1 = g_2 = g$, the transition temperature is given by $T_c \sim W \exp[-\frac{1}{(1+\lambda_J) g N(0)}]$, so the internal Josephson coupling enhances the coupling constant $gN(0)$ by a factor $(1 + \lambda_J)$.

In a strong coupling picture, tao-pairing is expected to be driven by superexchange processes, giving rise to Kugel-Khomskii type $J_1 - J_2$ interactions involving both spin and orbital exchange [21]. A decomposition of these terms will generally give BCS pairing terms in all the irreducible representations of the point group symmetry of the lattice, but the A_1 and A_2 tao states are then expected to exhibit the highest temperature instability thanks to the enhancement effect of the internal Josephson coupling.

We end with a discussion of the possible implications of tao-pairing. The tao scenario provides a mechanism for understanding how singlet superconductivity can avoid the strong Coulomb repulsion on the iron sites, namely through the locally d-wave character of its two pairing channels. At the same time, the scenario naturally accounts for absence of nodes in the 11-systems that only have electron pockets around the M points. There are a number of well established features of the experiments, such as the the absence of a Hebel-Slichter peak in NMR measurements [18, 19], and the observation of resonance peaks in the neutron scattering [22, 23] that are qualitatively consistent with the d-wave character of tao pairing, but have yet to be studied in detailed calculation. We have also not yet carried out a detailed study of the interaction of tao pairing with the Coulomb interaction.

In 3D multi-layer iron systems, tao pairing can in principle occur in four different global symmetry representations, A_1, A_2 and the staggered A_1^* and B_1^* representations, driven by interlayer physics that break the local inversion symmetry of the layers. The uniform A_g (s-wave) symmetries would appear to be the best candidate scenarios: driven by a strong in plane Josephson coupling, rather than a weaker inter-plane effect we expect these paired states to exhibit the greatest enhancement of T_c. Moreover, this scenario allows us to understand the observed c-axis tunneling into s-wave superconductors [11]. The A_1 state appears to possess the most isotropic gap (see Fig. 2 & 3), and would appear most consistent with STM experiments [24].

The staggered d-wave A_1^* and B_1^* states may become relevant to systems with strong interplane coupling. Many experiments suggest a multi-gap character to the superconducting condensate, including STM [24, 25], ARPES experiments [26], and the observation of a cross-over in the NMR relaxation rate from $\frac{1}{T_1}$ from T^3 at high temperatures to T^5[18, 19] behavior at low temperatures. This is consistent with the formation of a staggered A_1^* or B_1^* tao condensate in which the presence of the staggered d-wave gap $\Delta_{xyz} = \Delta_1 s_x s_y s_z$ will lead to out-of-plane point nodes. The development of these nodes would naturally account for the observation of a T^5 dependence in $\frac{1}{T_1}$ measurements in NMR experiments.

One of the interesting consequences of the theory, is that it predicts the condensation of pairs with an internal chirality ν. Pairs of reversed chirality, generated by anti-phase fluctuations of the two gaps are expected to then lead to a low-lying Leggett mode [27, 28] that will be Raman-active. There should also be higher-energy excitations of Cooper pairs of a different symmetry, for e.g. from A_1 to B_1, which will couple to corresponding Raman modes. The emergence of these low-lying "failed d-wave" excitations below T_c is key property of the tao-condensate.

A second aspect of the hidden chirality, is its topological character. An analysis of the symmetries of the pairing Hamiltonian shows that it lies in the "CI" class of topological superconductors [29]. In two dimensions, these states are topologically trivial and are not expected to exhibit edge states. However, the three dimensional extension of these pairing states does contain a topological Z invariant which allows for the possibility of non-trivial surface Andreev states.

In conclusion, symmetry analyses of the iron-based superconductors lead us to predict the existence of a new class of spin singlet, tetrahedral and orbital triplet pairing ("tao pairing"), in which a topologically non-trivial combination of locally d_{xy} and $d_{x^2-y^2}$ paired states gives rise to a fully gapped excitation spectrum. This novel state utilizes two new quantum iso-spins, providing an interesting new candidate symmetry for the fully gapped iron-based superconductors.

We gratefully acknowledge discussions with Girsh Blumberg, J. C. Seamus Davis, Matthew Foster, Gabriel Kotliar, Joerg Schmalian, and Manfred Sigrist on aspects of this work. This work is supported by DOE grant DE-FG02-99ER45790.

[1] Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, J. Am. Chem. Soc. **130**, 3296 (2008).

[2] P. J. Hirschfeld, M. M. Korshunov, and I. I. Mazin, Rep. Prog. Phys. **74**, 124508 (2011).

[3] J. Paglione and R. Greene, Nat. Phys. **6**, 645 (2010).

[4] M. M. Qazilbash, J. J. Hamlin, R. E. Baumbach, L. Zhang, D. J. Singh, M. B. Maple, and D. N. Basov, Nat. Phys. **5**, 647 (2009).

[5] C. Bourbonnais and D. Jerome, Interacting electrons in quasi-one-dimensional organic superconductors,

edited by A. G. Lebed, Vol. 110 (Springer, Heidelberg, 2008) pp. 357–412.

[6] S. Lefebvre, P. Wzietek, S. Brown, C. Bourbonnais, D. Jérome, C. Mézière, M. Fourmigué, and P. Batail, Phys. Rev. Lett. **85**, 5420 (2000).

[7] C. Pfleiderer, Rev. Mod. Phys. **81**, 1551 (2009).

[8] C. C. Tsuei and J. R. Kirtley, Phys. Rev. Lett. **85**, 182 (2000).

[9] A. P. Mackenzie and Y. Maeno, Rev. Mod. Phys. **75**, 657 (2003).

[10] I. I. Mazin and J. Schmalian, Physica C **469**, 614 (2009).

[11] X. Zhang, Y. S. Oh, Y. Liu, L. Yan, K. H. Kim, R. L. Greene, and I. Takeuchi, Phys. Rev. Lett. **102**, 147002 (2009).

[12] T. Hanaguri, S. Niitaka, K. Kuroki, and H. Takagi, Science **328**, 474 (2010).

[13] C. W. Hicks, T. M. Lippman, M. E. Huber, Z.-A. Ren, J. Yang, Z.-X. Zhao, and K. A. Moler, J. Phys. Soc. Jpn. **78**, 013708 (2009).

[14] Y. Zhang, L. X. Yang, M. Xu, Z. R. Ye, F. Chen, C. He, H. C. Xu, J. Jiang, B. P. Xie, J. J. Ying, X. F. Wang, X. H. Chen, J. P. Hu, M. Matsunami, S. Kimura, and D. L. Feng, Nat. Mater. **10**, 273 (2011).

[15] D. Liu, W. Zhang, D. Mou, J. He, Y.-B. Ou, Q.-Y. Wang, Z. Li, L. Wang, L. Zhao, S. He, Y. Peng, X. Liu, C. Chen, L. Yu, G. Liu, X. Dong, J. Zhang, C. Chen, Z. Xu, J. Hu, X. Chen, X. Ma, Q. Xue, and X. J. Zhou, Nat. Commun. **3**, 931 (2012).

[16] T. A. Maier, S. Graser, P. J. Hirschfeld, and D. J. Scalapino, Phys. Rev. B **83**, 100515 (2011).

[17] X.-P. Wang, P. Richard, X. Shi, A. Roekeghem, Y.-B. Huang, E. Razzoli, T. Qian, E. Rienks, S. Thirupathaiah, H.-D. Wang, C.-H. Dong, M.-H. Fang, M. Shi, and H. Ding, Europhys. Lett. **99**, 67001 (2012).

[18] N. Terasaki, H. Mukuda, M. Yashima, Y. Kitaoka, K. Miyazawa, P. M. Shirage, H. Kito, H. Eisaki, and A. Iyo, J. Phys. Soc. Jpn. **78** (2009).

[19] M. Yashima, H. Nishimura, H. Mukuda, Y. Kitaoka, K. Miyazawa, P. M. Shirage, K. Kihou, H. Kito, H. Eisaki, and A. Iyo, J. Phys. Soc. Jpn. **78** (2009).

[20] J. Hu and N. Hao, Phys. Rev. X **2**, 021009 (2012).

[21] K. Kugel and D. Khomskii, Sov. Phys. Usp. **25**, 231 (1982).

[22] D. S. Inosov, J. T. Park, P. Bourges, D. L. Sun, Y. Sidis, A. Schneidewind, K. Hradil, D. Haug, C. T. Lin, B. Keimer, and V. Hinkov, Nat. Phys. **6**, 178 (2010).

[23] A. D. Christianson, E. A. Goremychkin, R. Osborn, S. Rosenkranz, M. D. Lumsden, C. D.

Malliakas, I. S. Todorov, H. Claus, D. Y. Chung, M. G. Kanatzidis, R. I. Bewley, and T. Guidi, Nature **456**, 930 (2008).

[24] J. E. Hoffman, Rep. Prog. Phys. **74**, 124513 (2011).

[25] M. P. Allan, A. W. Rost, A. P. Mackenzie, Y. Xie, J. C. Davis, K. Kihou, C. H. Lee, A. Iyo, H. Eisaki, and T. M. Chuang, Science **336**, 563 (2012).

[26] H. Ding, P. Richard, K. Nakayama, K. Sugawara, T. Arakane, Y. Sekiba, A. Takayama, S. Souma, T. Sato, T. Takahashi, Z. Wang, X. Dai, Z. Fang, G. F. Chen, J. L. Luo, and N. L. Wang, Europhys. Lett. **83**, 47001 (2008).

[27] A. J. Leggett, Prog. Theor. Phys. **36**, 901 (1966).

[28] G. Blumberg, A. Mialitsin, B. S. Debbis, M. V. Klein, N. D. Zhigadlo, and J. Karpinski, Phys. Rev. Lett. **99**, 227002 (2007).

[29] A. Schnyder, S. Ryu, A. Furusaki, and A. Ludwig, Physical Review B **78**, 195125 (2008).